

PAPER DETAILS

TITLE: Mineral Based Boards made from Lignocellulosic Wastes: 1st Part - Physical And Mechanical Properties

AUTHORS: Ömer YALÇIN, Ali İhsan KAYA, Halil Turgut SAHİN

PAGES: 142-149

ORIGINAL PDF URL: <https://dergipark.org.tr/tr/download/article-file/1057413>

**Mineral Based Boards made from Lignocellulosic Wastes:
1st Part - Physical And Mechanical Properties**Ömer Ümit YALÇIN¹, Ali İhsan KAYA^{2*}, Halil Turgut ŞAHİN¹¹Isparta University of Applied Sciences, Forestry Faculty, Isparta-Turkey²Burdur Mehmet Akif Ersoy University, Technical Sciences Vocational School, Burdur-Turkey

Geliş Tarihi (Received): 17.04.2020, Kabul Tarihi (Accepted): 23.05.2020

✉ Sorumlu Yazar (Corresponding author*): aikaya@mehmetakif.edu.tr

☎ +90 248 2134563 📠 +90 248 2134598

ABSTRACT

Lignocellulosic waste of eggplant and tomato stalks has used with minerals of olivine and dolomite at various proportions to produce experimental particleboards that have subject to some physical and mechanical tests. In this regards, Thickness Swelling in water (TS, %), Water Absorption (WA, %), Internal Bond (IB), Bending Strength (MOR), Modulus of Elasticity (MOE) and color properties (CIE, L, a, b) of the boards were examined. It has observed that type and content of minerals effects TS and WA of test panels. Besides the internal bond strength values of the test boards that were generally higher than 0.28 N/mm², it was found that the bending resistance properties of the boards produced with tomato stalk/dolomite mixture show higher MOR values in similar manufacturing conditions than those produced with olivine. However, boards prepared from tomato/eggplant stalks proportions with dolomite/olivine mixture show lower MOE values than the standard value in all production conditions.

Keywords: Lignocellulosic waste, mechanical properties, particleboard, physical properties**Lignoselülozik Atıklardan Üretilen Mineral Esaslı Levhalar:
1. Bölüm - Fiziksel ve Mekanik Özellikler****ÖZ**

Lignoselülozik atık olarak değerlendirilen patlıcan ve domates sapları ile olivin ve dolomit minerallerinin belli oranlarda karışımı ile yonga levha üretimi olanakları bazı fiziksel ve mekanik testlerle araştırılmıştır. Bu bağlamda levhaların kalınlık artım oranı (%), su emme miktarı (%), yüzeye dik çekme direnci, eğilme direnci (MOR), elastikiyet modülü (MOE) ve renk özellikleri (CIE, L, a, b) üzerine araştırma yapılmıştır. Minerallerin türü ve içeriğinin test örneklerinin kalınlık artım ve su alma miktarlarını etkilediği gözlemlenmiştir. Test levhalarının yüzeye dik çekme direnç değerlerinin genellikle standart değer olan 0.28 N/mm² daha yüksek olduğu, ayrıca domates sapı/dolomit karışımı ile üretilen levhaların eğilme direnci özelliklerinin, benzer imalat koşullarında olivinle üretilenlere göre daha yüksek MOR değerleri gösterdiği bulunmuştur. Bununla birlikte, domates/patlıcan sapları ile dolomit/olivin karışımından oluşan levhaların tüm üretim koşullarında standart değerden daha düşük MOE değerleri gösterdiği anlaşılmıştır.

Anahtar Kelimeler: Lignoselülozik atık, mekanik özellikler, yonga levha, fiziksel özellikler

INTRODUCTION

Woody parts of some annual plants have become important source for producing particle boards (Youngquist et al., 1994). Numerous studies has already conducted for many non-wood sources in order to explaine their properties and suitable to bio-composite manufacturing. Some of the examples could be given as; kenaf plant (Muehl et al., 1999), wheat and rice stalks (Mantanis et al., 2000), sugar cane residues (Wu, 2001), vine pruning residues (Ntalos and Grigoriou 2002), Kiwi (*Actinidia sinensis* planch.), pruning wastes (Nemli et al., 2003), sunflower stalk/wood mixture (Bektaş et al., 2005), cotton carpels (Alma et al., 2005), some vegetable waste stalks (tomato, pepper, eggplant) (Karakuş 2007), fruit pruning's (apple, apricot, cherry) wastes (Arslan et al., 2008), were investigated and the possibilities of board production were reported with some important results . It has predicted that economically unsound parts of some plants that have obtained after agricultural process such as; agave, hazelnut, peanut shells, cotton seeds, sunflower stalks, sugar cane residues could be useful in forest products industry as wood substitute material (Atchison, 1993; Rowell, 1997; Young, 1997).

However the usage of inorganic materials such as olivine or dolomite, in the production of bio-based composite boards are limited. These materials are usually utilized in large quantities in iron-steel processing, ceramic manufacturing, paint additives, fertilizer for plants, glass producing and construction industry (Peiwei et al., 2008). Although these mineral sources could be available in nature in large quantity, only limited experiments conducted and found to be some positive results within board properties (Peiwei et al., 2008).

It was reported that the addition of dolomite as filler to the structure of HDF boards that produced from beech-pine fibers, clearly effects some physical and mechanical properties that water absorption, thickness swelling, MOR, MOE and surface roughness lowered in some level while the fire resistance properties increased (Özdemir, 2016; Özdemir et al., 2016).

There is very limited research conducted on olivine and dolomite effects on particleboards properties. However, in this study, a basic approach was used to understand the effects of two similar minerals (olivine and dolomite) on experimental particleboards made from two different waste of bio materials (tomato and eggplant) with certain proportions.

MATERIALS AND METHODS

Eggplant and tomato stalks (as waste material) were used for particleboard production obtained from the greenhouses of Antalya province, Turkey. These are collected and separated from soils and other substances after the main production in greenhouses. The minerals of olivine and dolomite materials were collected from Isparta-Aksu mining sites in Turkey. The urea-formaldehyde adhesive was supplied from a commercially operate a particle board plant.

The eggplant and tomato stalks were turn to particles (1-3 cm) with laboratory type hammer mill then dried in the oven at 105 (\pm 3°C) temperatures until they reached 2-3% moisture content. The 65% urea-formaldehyde glue and 20% ammonium chloride hardener were used in the production of the boards. The glue was applied 10% and hardener was 1% in the test boards by weight based on oven dry material. Metal mold plates with the dimensions of 40 x 40 cm and 10 mm was used to prepare the board paste. Then it were pressed for 8 minutes under 2.5N / mm² at 170-180 °C with laboratory type electrically heated press. Boards were kept between metal plates after the end of pressing process and then climatized. The experimental panels were conditioned at 23°C and 65% relative humidity and samples were cut to determine the IB (Internal Bond), MOE and MOR (Modulus of Elasticity and Rupture), TS (Thickness Swelling after two and 24 hours immersion in water) and The Water Absorption (WA, %), in accordance with TS EN 310 (1999), TS EN 319 (1999) and TS EN 317 (1999) standards, respectively. The experimental boards were prepared with given codes in this study was summarized in Table 1.

Table 1. Code numbers and mixture proportions (gr) of materials (**0-5:** Tomato stalks (%), **a-f:** Eggplant stalks(%), **X:** Dolomit, **Y:** Olivine)

Board Code	Dolomite (%)	Tomato Stalks (%)	Board Code	Olivin (%)	Tomato Stalks (%)
X ₀	0	100	Y ₀	0	100
X ₁	10	90	Y ₁	10	90
X ₂	20	80	Y ₂	20	80
X ₃	30	70	Y ₃	30	70
X ₄	40	60	Y ₄	40	60
X ₅	50	50	Y ₅	50	50
Board Code	Dolomite (%)	Eggplant Stalks (%)	Board Code	Olivin (%)	Eggplant Stalks (%)
X _a	0	100	Y _a	0	100
X _b	10	90	Y _b	10	90
X _c	20	80	Y _c	20	80
X _d	30	70	Y _d	30	70
X _e	40	60	Y _e	40	60
X _f	50	50	Y _f	50	50

Measurements were conducted in Isparta University of Applied Sciences, Forest Product Engineering Research and Application Laboratory.

The color characteristics were measured by X-Rite SP-68 spectrophotometer. The experimental boards were kept in external atmospheric conditions for 60 days and according to CIE L * a * b * (1976) standard, differences (Delta values) were calculated as surface color values.

An ANOVA general linear model procedure was employed for data to interpret interaction of the panels manufactured. Duncan test was used to make comparison among board types for each property tested if the ANOVA found significant.

RESULTS AND DISCUSSIONS

The water absorption (WA) properties of boards in water (2.0 and 24 hours) are shown in Table 2. It is clearly seen that more less similar results were observed for water absorption properties of the experimental boards made from tomato and eggplant stalk with dolomite and olivine as mineral filler in mixture. However, the lowest amount of water absorption were observed on X₄ type board (40% dolomite/60% tomato stalk mixture board) as 62.70%. It is important to note that increasing mineral content have been found to improve the water absorption properties in some levels, but especially the boards produced with dolomite rather than olivine at similar manufacturing conditions.

It was shown from statistical data that F value of dolomite-tomato mixture type boards was found 9.114

(P = 0.009) on water absorption properties. Likewise F value of dolomite-eggplant mixture type boards was observed as 8.054 (P=0.012). According to these results, significant difference was found between board mixing rates (X₀₋₅/X_{a-f}) and water intake properties. The similar F value results were seen in olivine-eggplant (Y_{a-i}) mixture as 23.913 (P=0.001). But olivine-tomato type boards were found statistically insignificant.

Table 3 shows the thickness swelling (TS) values of boards in water. It can be realized that the thickness swelling values of the boards were found higher than the standard value of 12.5% in all conditions. However the lowest TS value 12.80% was observed with Y_f that produced from 50% eggplant stalk and 50% mineral olivine. Moreover the highest TS value of 50.59% was found in X_a type board which produced only by eggplant stalks.

It seems that presence of both dolomite and olivine as mineral filler have negative effect on TS properties. Therefore, it seems that mineral increment can not block the penetration into the board, resulting in higher TS properties.

F value of dolomite-tomato mixture type boards was found 38,034 (P=0,000) for TS properties. Similarly, F value of olivine-tomato mixture and olivine-eggplant type boards were found as 6,526 (P=0,020), 14,353 (P=0,003) respectively. According to these results, significant difference was seen between board mixing rates (X_{a-f}/Y₀₋₅/Y_{a-f}) and thickness swelling properties. However dolomite-tomato type boards were found statistically insignificant.

Table 2. The water absorption(%) values of boards

Board Code	WA (2h)	WA (24 h)	F value	Board Code	WA (2h)	WA (24 h)	F value
X ₀	59.92	90.00 (bc)	9.114**	Y ₀	59.92	90.00(a)	2.111^(ns)
X ₁	77.36	98.99 (c)		Y ₁	65.15	90.19(a)	
X ₂	63.25	79.93 (ab)		Y ₂	63.08	83.88(a)	
X ₃	48.41	62.73 (a)		Y ₃	57.31	78.10(a)	
X ₄	48.99	62.70 (a)		Y ₄	67.94	87.46(a)	
X ₅	48.83	63.79 (a)		Y ₅	57.35	78.47(a)	
X _a	76.36	110.30 (b)	8.054*	Y _a	76.36	110.30(c)	23.913**
X _b	67.81	105.05 (b)		Y _b	81.34	112.69(c)	
X _c	61.28	88.34 (ab)		Y _c	72.58	95.25(b)	
X _d	37.46	66.55 (a)		Y _d	56.63	74.41(a)	
X _e	75.87	106.12 (b)		Y _e	72.90	98.42(b)	
X _f	50.22	77.07 (a)		Y _f	69.08	92.87(b)	

Note: (***) means 99.9% confidence level, (ns) is statistically insignificant, (a, b, c, d, e) means homogeneous groups.

Table 3. The thickness swelling (%) properties of boards in water

Board Code	TS (2h)	TS (24 h)	F Value	Board Code	TS (2h)	TS (24 h)	F Value
X ₀	25.69	37.90(a)	2.377^(ns)	Y ₀	25.69	37.90(b)	6.526*
X ₁	25.83	32.00(a)		Y ₁	25.86	34.86(b)	
X ₂	24.20	30.49(a)		Y ₂	21.70	28.87(b)	
X ₃	22.64	27.48(a)		Y ₃	27.09	37.30(b)	
X ₄	18.95	23.85(a)		Y ₄	10.85	14.97(a)	
X ₅	20.84	26.51(a)		Y ₅	21.69	28.48(b)	
X _a	26.18	50.59(c)	38.034***	Y _a	36.39	50.59(bc)	14.353**
X _b	19.37	36.60(c)		Y _b	26.18	38.82(c)	
X _c	25.65	39.61(c)		Y _c	27.91	33.92(b)	
X _d	10.21	23.23(b)		Y _d	20.25	26.23(ab)	
X _e	11.48	14.86(a)		Y _e	12.12	15.81(a)	
X _f	10.53	14.71(a)		Y _f	10.78	12.80(a)	

Note: (***) means 99.9% confidence level, (ns) is statistically insignificant, (a, b, c, d, e) means homogeneous groups.

Table 4 shows the comparative internal bond (IB), modulus of rupture (MOR) and modulus of elasticity (MOE) values of boards produced from tomato stalk /eggplant stalk / dolomite and olivine mixture.

It was realized that the highest internal bond (IB) value was observed in the 30%dolomite,70% tomato stalk mixture (X₃) as 0.81 N/mm² and the lowest IB in 100% eggplant stalk mixture (X_a) as 0.22 N/mm².

Figure 1 shows that approximately all boards have higher internal bond (IB) strength value than the standard value of 0.28 N/mm². It was seen that mineral fillers especially dolomit rather than olivine could positive effect to IB properties. This is very interesting results considering IB strength developments in composite network. It could be hypothesised that the mineral fillers

may not absorb the adhesive as others that effects further adhesive available for lignocellulosic. However, tomato and eggplant stalks's porosity is higher than minerals that could be possible to better alignment in network structure and absorp sy nthetic adhesive properly.

According to the ANOVA analysis results for IB bond properties of boards, significant differences with 99.9% confidence level were found between (X₀₋₅/Y₀₋₅/Y_{a-f}) type board mixing rates and modulus of rupture (MOR). Likewise, 99% confidence level was observed on eggplant-dolomite mixture type boards. Moreover modulus of elasticity (MOE) results were found statistically significant in Y_{a-f} (99.9%), X_{a-f}/Y₀₋₅ (99%) but X₀₋₅ type samples were found statistically insignificant.


Table 4. The mechanical strength properties of experimental boards (MOE, MOR, and IB)

Board Code	IB (MPa)	F value	MOR (MPa)	F value	MOE (MPa)	F value
X ₀	0.35(a)	7.862***	8.46(c)	7.216***	1367.9(a)	0.889(ns)
X ₁	0.73(cd)		8.51(c)		835.3(a)	
X ₂	0.58(bc)		6.69(bc)		693.5(a)	
X ₃	0.81(d)		6.21(bc)		694.7(a)	
X ₄	0.80(cd)		4.88(ab)		689.9(a)	
X ₅	0.53(ab)		3.23(a)		1056.1(a)	
X _a	0.22(a)	5.046**	3.38(a)	4.998**	486.34(a)	5.542**
X _b	0.29(ab)		5.95(bcd)		660.14(ab)	
X _c	0.30(ab)		6.67(cd)		1212.36(c)	
X _d	0.40(c)		7.02(d)		915.66(bc)	
X _e	0.34(ab)		4.10(ab)		655.43(ab)	
X _f	0.38(bc)		4.81(abc)		1242.69(c)	
Y ₀	0.35(a)	3.131*	8.46(d)	10.458***	1367.9(d)	4.946**
Y ₁	0.74(b)		7.44(cd)		1075.8(bc)	
Y ₂	0.67(b)		5.85(bc)		1119.7(bc)	
Y ₃	0.68(ab)		3.83(ab)		830.2(ab)	
Y ₄	0.64(ab)		2.84(a)		647.3(ab)	
Y ₅	0.54(ab)		2.49(a)		508.9(a)	
Y _a	0.22(a)	4.596**	3.38(ab)	8.350***	486.34(a)	7.829***
Y _b	0.29(ab)		4.81(bc)		728.4(a)	
Y _c	0.37(bc)		7.76(d)		1139.6(b)	
Y _d	0.43(c)		6.64(cd)		1037.1(b)	
Y _e	0.24(ab)		5.06(bc)		641.8(a)	
Y _f	0.35(ab)		2.71(a)		534.8(a)	

Note: (***) means 99.9% confidence level, (ns) is statistically insignificant, (a, b, c, d, e) means homogeneous groups.

Figure 2 shows bending strength (MOR) and modulus of elasticity (MOE) values of boards manufactured from various proportions of tomato/eggplant stalks with

mineral fillers. It could be seen that the addition of both dolomite and olivine substances in the board affected these values are negatively.

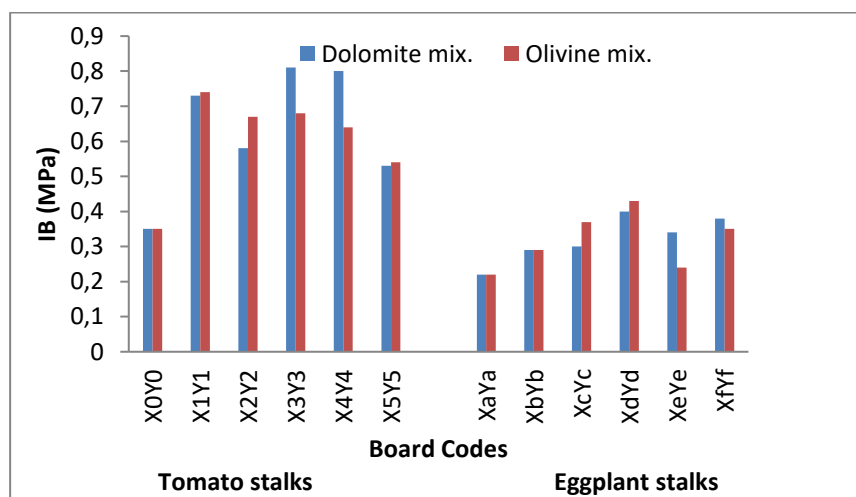**Figure 1.** The internal bond (IB) properties of boards

It was observed that the highest modulus of rupture was found 8.51 N/mm² in the 90% tomato/10% dolomite (X₁) board and the lowest in the 50% olive/50% tomato stalks (Y₅) board with 2.49 N / mm². It has been found that dolomite based boards have usually higher MOR values than those produced with olive under the same production conditions. It can be seen that increasing mineral proportion effects on lowering MOR values in general.

However, it was shown that the modulus of elasticity (MOE) values of all boards were found lower than the standard value of 1600 N/mm². Moreover, the lowest MOE value was calculated in 100% eggplant stalk board sample as 486.34 N / mm² and the highest value was in 100% tomato stalk board sample as 1367.9 N/mm².

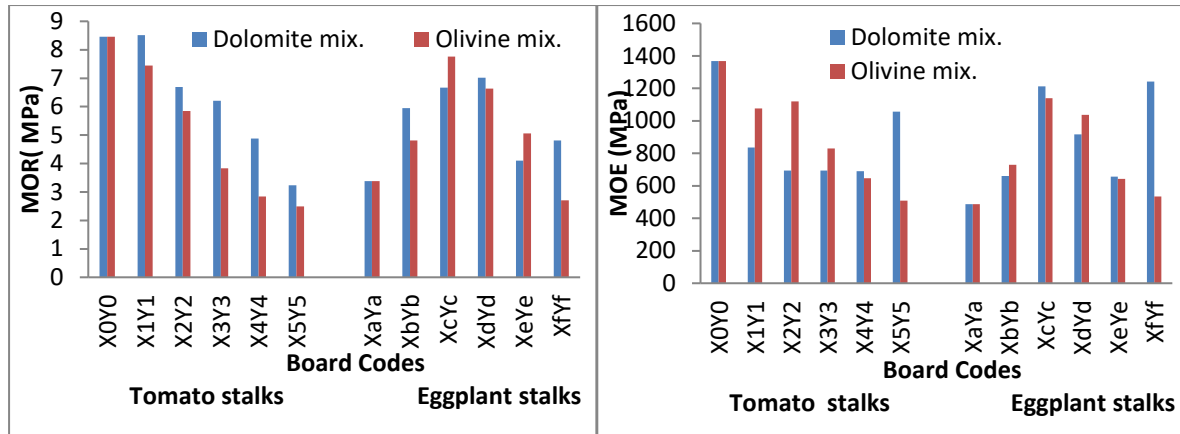


Figure 2. Modulus of rupture (MOR) and modulus of elasticity(MOE) properties of boards

The bending strength and elasticity of bio composite materials are sensitive to bonding potential as well as the relative bonded area, which originates from the surface properties of fillers and particles in matrices that other properties (lignocellulosic particle dimensions) remain intact. Although in certain manufacturing conditions, boards show higher IB strength properties than standard values, that show considerably lower MOR and MOE properties than standard values. It is clear that mineral fillers could effects fibre flexibility and bonding potential of particles in matrix structure.

Test boards were kept for 60 days under external atmospheric conditions for evaluating weathering performances and then the differences of surface color values were determined. Color changing (Δ) are shown

in Figure 3. Although it is an easy and useful method to determine the basic color values of the materials, the explanation of each color parameter (CIE L *, a *, b *) is quite complicated. However, examination of the total color difference (ΔE) value is important in terms of providing information about the way of change.

It was measured that the maximum color differences were observed in X₀ (100% tomato) type board as 12.81% and X_a (100% eggplant) type board as 13.67% . However, the lowest changing was observed in X_c type board as $\Delta E = 1.15$ and Y₅ type board as $\Delta E = 2.30$ respectively. It could understood from Figure 3 that mineral in higher proportions in mixtures in all types was decreased the color changings.

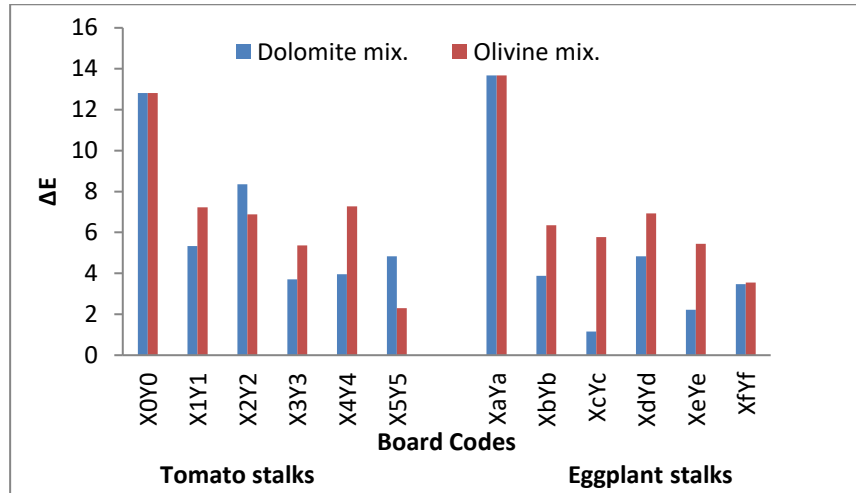


Figure 3. Color characteristics of the boards

CONCLUSIONS

In this study, the usability of mineral substances which are dolomite and olivine minerals with tomato and eggplant stalks as greenhouse waste in the board structure was investigated. It was understood that tomato and eggplant stalks as lignocellulosic waste materials could use in the production of composite boards with mineral mixture in some proportions.

However, addition of the hydrophobic mineral substances to mixture improved thickness swelling and water absorbtion properties in water. But, in some cases dolomite and olivine minerals contribute negative effects such as bending strength and modulus of elasticity. Therefore, the mechanical properties of boards are not between acceptable level for composite panels such as construction panels, however it can use some places where is not strength neccesity such as; insulation applications, outdoor panels or sidings.

It is important that large particle size of the mineral substances and the heterogeneous distribution in the board composition negatively affected the mechanical properties. Hence, the application of mineral materials should improve efficiently then required levels can be achieved.

REFERENCES

- Alma, M.H., Kalaycıoğlu, H., Bektaş, İ., Tutuş, A. (2005). Properties of Cotton Carpel Based Particleboards, *Industrial Crops and Products*, 22 (2): 141-149.
- Arslan, M.B., Karakuş, B., Güntekin, E. (2008). Tarımsal atıklardan lif ve yonga levha üretimi. *ZKÜ Bartın Orman Fakültesi Dergisi*, 12: 54-62.
- Atchison, J.E. (1993). Data on non-wood plant fibers, In: *Properties of Fibrous Raw Materials and Their Preparation for Pulping*, M.J. Kocurek (Ed), Pulp and paper

- manufacture Vol.3, Joint Textbook Committee of the Paper Industry, Tappi Press, Atlanta, GA. 157-174.
- Bektaş, İ., Guler, C., Kalaycıoğlu, H., Mengeloğlu, F., Nacar, M. (2005). The manufacture of particleboards using sunflower stalks and poplar wood. *Journal of Composite Materials*, 39: 467-473.
- Eroğlu, H., Usta, M. (2000). *Lif Levha Üretim Teknolojisi*, KTÜ Orman fakültesi ders notu, Trabzon.
- Kalaycıoğlu, H., Deniz, I., Hızıroğlu, S. (2005). Some of the properties of particleboard made from paulownia. *Journal of Wood Science*, 51:410-414.
- Karakuş, B. (2007). Çeşitli bitkisel sera atıklarının yonga levha üretiminde değerlendirilmesi. *SDÜ. Fen Bilimleri Enstitüsü, Yüksek Lisans Tezi*, Isparta, 80-85p.
- Maloney, T.M. (1996). The Family of Wood Composite Materials, *Forest Products Journal*, 46 (2): 19-26.
- Mantanis G., Nakos P., Berns J., Rigal L. (2000). Turning Agricultural Straw Residues Into Value-Added Composite Products: A New Environmentally Friendly Technology. In: *Proc. of the 5th International Conference on Environmental Pollution*, Aug. 28-31, 2000, Aristotelian University, Thessaloniki, Greece, 840-848p.
- Moloney, T.M. (1977). *Modern Particleboard and Dry-Process Fiberboard Manufacturing*, Miller Freeman Publications, San Francisco.
- Muehl, J.H., Krzysik, A. M., Youngquist, J. A., Chow, P. and Bao, Z. (1999). Performance of Hardboards Made from Kenaf, In: *Kenaf Properties, Processing and Products*, T. Sellers, vd., (Eds), 367-379p.
- Nemli, G., Kirci, H., Serdar, B., Ay, N. (2003). Suitability of Kiwi (*Actinidia sinensis planch.*) Prunings for Particleboard Manufacturing. *Industrial Crops and Products* 17: 39-46.
- Ntalos, G., A., Grigoriou, A., H. (2002). Characterization and Utilisation of Vine Prunings as a Wood Substitute for Particleboard Production. *Industrial Crops and Products*, 16: 59-68.
- Özdemir, F. (2016). Yüksek Yoğunluklu Lif Levhanın Bazı Özellikleri Üzerine Dolomit Mineralinin Etkisinin Araştırılması. *Kahramanmaraş Sütçü İmam Üniversitesi Mühendislik Bilimleri Dergisi* 19: 93-98.

- Özdemir, F., Tutuş, A., Çiçekler, M. (2016). Effect of Dolomite Mineral on Surface Roughness of High Density Fiberboard (HDF). In 2nd International Furniture Congress. 498-501p.
- Peiwei, G., Xiaolin, L., Shaochun, J., Hui, Z., Chunxing, G. (2008). Using a New Composite Expansive Material to Decrease Deformation and Fracture of Concrete. *Materials Letters*, 62(1): 106-108.
- Rials, G. T., Wolcott, M.P. (1997). Physical and mechanical properties of agro-based fibers, In: *Paper and composites from agro based resources*, Rowell, R.M., Young, R.A., Rowell, J.K. (Eds), CRC Press, Inc, Boca Raton, Florida. 63-81p.
- Rowell, R.M. (1997). Opportunities for Composites from Agro-based Resources, In: *Paper and Composites from Agro-Based Resources*, Rowell, R.M., Young, R.A., Rowell, J.K., (Eds), CRC Press, Inc, Boca Raton, Florida. 249-300p.
- Suchland, O., Woodson, G. (1987). *Fiberboard Manufacturing Practices in the United States*, Department of Agriculture Forest Service Agriculture Handbook No. 640, Washington DC.
- Sahin, H.T., Arslan, M.B. (2011). Weathering Performance of Particleboards Manufactured from Blends of Forest Residues with Red pine (*Pinus brutia*) Wood, *Maderas: Ciencia y Tecnologia*, 13 (3): 337-346.
- Sahin, H.T., Arslan, M.B. (2013). Properties of Orchard Pruning and Suitability for Composite Production, *Science and Engineering of Composite Materials*, 20 (4): 337-342.
- Şahin, H. T. (2006). Kağıt ve kompozit ürünleri için lignoselülozik hammadde kaynakları, *Orman Mühendisliği*, 43: 4-6.
- Wu, Q. (2001). Comparative Properties of Bagasse Particleboard. *Proc. of the Symposium on Utilization of Agricultural and Forestry Residues*, Oct. 31-Nov. 3, 2001, Nanjing Forestry University, Nanjing, China, 277-284p.
- Young, R.A. (1997). Pulp and paper, In: Rowell, R. M., Young, R.A., Rowell, J.K. (Eds), *Paper and Composites from Agro-based Resources*, CRC Press Inc., Boca Raton, Florida.
- Youngquist, J.A., English, B.E., Scharmer, R.C., Chow, P., Shook, S.R. (1994). Literature Review on Use of Nonwood Plant Fibers for Building Materials and Panels, USDA Forest Service, General Technical Report, FPL-GTR 80, Madison, WI.