

PAPER DETAILS

TITLE: Environmental impact of bio-briquettes produced from agricultural residues concerning to CO2 emissions

AUTHORS: Gürkan GÜRDİL

PAGES: 217-224

ORIGINAL PDF URL: <https://dergipark.org.tr/tr/download/article-file/1098611>



Environmental impact of bio-briquettes produced from agricultural residues concerning to CO₂ emissions

Tarımsal artıklardan üretilen biyo-briketlerin CO₂ emisyonları açısından çevresel etkisi

Gürkan Alp Kağan GÜRDİL¹ 

¹Ondokuz Mayıs University, Department of Agricultural Machines and Technologies Engineering, Faculty of Agriculture, Samsun, TURKEY.

MAKALE BİLGİSİ / ARTICLE INFO

Makale tarihçesi / Article history:

DOI: [10.37908/mkutbd.735750](https://doi.org/10.37908/mkutbd.735750)

Geliş tarihi /Received:11.05.2020

Kabul tarihi/Accepted:27.05.2020

Keywords:

Biofuel, briquette, carbon dioxide, environment, flue gas, residue.

✉ Corresponding author: G. A. K. GÜRDİL

✉: ggurdil@omu.edu.tr

ÖZET / ABSTRACT

Aims: This study examined the flue gas emissions of bio-briquettes produced from agricultural residues.

Methods and Results: The briquettes were produced from residues of tea (*Camellia sinensis*) processing plants, pruning residues of persimmon (*Diospyros kaki*), tomato (*Solanum lycopersicum*) stalk and pruning residues of peach (*Prunus persica*) tree. The residues were briquetted using a hydraulic briquetting machine with a horizontal course. Solid cylindrical briquettes were produced under different compression pressures ranging from 40 MPa to 240 MPa, with a moisture content of 10%-12% and having a particle size of 5 mm. Flue gas emissions of bio-briquettes were measured.

Conclusions: The results of the study showed that CO₂ emissions increased with increase in the briquetting pressures. The lowest CO₂ emission was (2.50%) obtained at 120 MPa pressure for the briquettes produced from tomato stalk residues, where the highest was (8.90%) at 240 MPa for the briquettes produced from peach tree pruning.

Significance and Impact of the Study: This study deals with the CO₂ emission of biomass resulted from residues/wastes from the intensive farming of tea (*Camellia sinensis*), persimmon (*Diospyros kaki*), tomato (*Solanum lycopersicum*) and peach (*Prunus persica*).

Atıf / Citation: Gürdil GAK (2020) Environmental impact of bio-briquettes produced from agricultural residues concerning to CO₂ emissions. *MKU. Tar. Bil. Derg.* 25(2) : 217-224. DOI: 10.37908/mkutbd.735750

INTRODUCTION

Energy is a vital element for the economic growth of countries and social life in today's society. However, the depletion of fossil fuel sources has started already and the demand for energy increasing day by day as the world's population increases. Fossil fuels such as petroleum, coal and natural gas meet the demand for world's energy (Wang and Sarkar, 2018). Given that the main task of the energy sector is to ensure the continuous availability of reasonably priced energy for a growing population and the emerging economy, it is clear that fossil-based fuel consumption should be

reduced and new and renewable energy sources should be investigated (Ültanır, 1996). Amongst the existing global challenges, indiscriminate burning of fossil fuels and the ensuing climate change impact due to CO₂ emissions are the most serious problems of 21st century. Of the renewable energy sources, bioenergy as sustainable and environmentally friendly alternative to the fossil fuels has stirred substantial research worldwide (Karaca, 2017). Biomass conversion processes have emerged as a rapidly growing field of science and technology endeavored to fulfil ever-growing energy deficit as well as reduce CO₂ emissions by 70–90% (Timung et al., 2015; Sohni et al., 2018).



Figure 1. Residues from a) tea, b) tomato, c) persimmon, d) peach

The issue of energy utilization of waste material is a subject of the International and European policy in the field of waste management (Malatak and Bradna, 2017). Biomass has received tremendous attention both in developed and developing countries as a renewable energy source (Grover and Mishra, 1996; Muazu and Stegemann, 2015; Karaca, 2019). Biomass energy, i.e. energy obtained from plant and animal-based natural

materials composed mainly of carbon-hydrate compounds (Ölçüm, 2006; Chen et al., 2011; Prakash and Karunanithi, 2008), represents a source of environmentally friendly and inexhaustible renewable energy. The energy use of waste biomass as a renewable source of energy has many positive aspects and helps solve problems not only ecological but also in agro-forestry (McBurney, 1995). The biomass-based fuels

contain almost no sulfur and sulfur dioxide emissions (Hajek et al., 2013). Other pollutants in emissions from waste biomass are favorable in comparison with emissions from fossil fuels (Malatak and Passian, 2011). Production of high-quality biofuels with good mechanical, chemical and energy properties is strongly desired (Ndindeng et al., 2015). Biomass, which includes agricultural residues, accounts for approximately two-thirds of all potential sources of renewable energy in Turkey (Angın and Şensöz, 2006), whose vast areas of agricultural production offer great potential in terms of renewable energy resources.

Agricultural residues produced out of huge agricultural productions everywhere on the world are becoming a very popular not only for organic material based fertilization but, also for producing renewable energy by means of biofuels. This study examined the CO₂ emission from cylindrical briquettes made of the residues of four different agricultural products tea (*Camellia sinensis*), persimmon (*Diospyros kaki*), tomato (*Solanum lycopersicum*) and peach (*Prunus persica*) (Figure 1). Full cylindrical briquettes were produced with a hydraulic briquetting machine under different compression pressures ranging from P: 40 MPa to 240 MPa, with a moisture content of M12 (M12: 10%-12%) and having a particle size of (PS: 5 mm). results revealed a close relation between the briquetting pressures and CO₂ emissions.

MATERIALS and METHODS

This study was conducted using residues from tea processing plants, tomato residues after harvesting and pruning residues from peach and persimmon gardens.

Briquetting

Briquetting, one of the densification technologies, is a fundamental and promising method for conversion of the biomass into solid biofuels (Hoover et al., 2014). It is achieved by forcing loose particles together into a larger, more compact and shaped form, by application of mechanical force to create particle-to-particle bonding (Kaliyan and Morey, 2010; Karunanithy et al., 2012). The residues of particular products were collected from the gardens, greenhouses and processing facilities and brought to workshop and laboratories of Agricultural Faculty at Ondokuz Mayıs University in Samsun Turkey. They were ground 5 mm by a 3 kW powered hammer mill consisting of 8 hammers rotating at a speed of 2,850 rpm. Then, they were sun dried under normal conditions until the M12 (M12: 10%-12%) was achieved as defined by standards (EN 14774-1, 2009; EN ISO 17225-3, 2015). Solid cylindrical briquettes were produced by a hydraulic type briquetting machine having a mold with a wall-thickness of 25 mm (Figure 2).

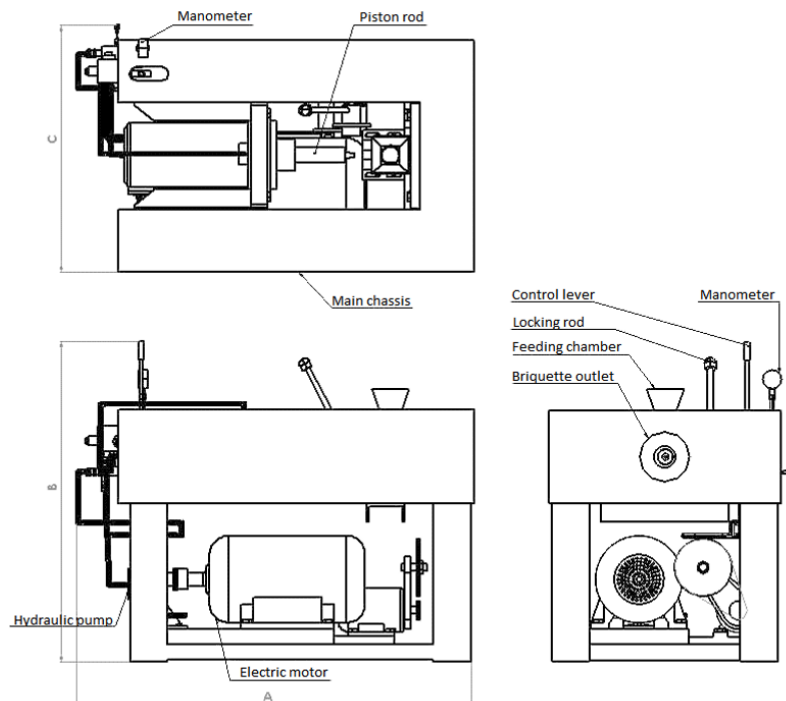


Figure 2. Hydraulic briquetting machine (A: 1280 mm; B: 1155 mm; C: 740 mm)

Flue gas emissions of briquettes

Briquettes were burned in a briquette stove and the flue-gas emissions during burning were measured using an Ecom EN2 flue-gas sensor. The probe of the device was installed approximately 1 m above the stove, and all readings were performed from this constant point as shown in Figure 3. The pellets were burned in a pellet stove with an auxiliary air flow. Flue gas emissions were

recorded after a regular burning of pellets were provided.

Data analysis was performed using the IBM SPSS Statistics 21 software. The normality analysis was performed with the Kolmogorov-Smirnov single sample test and the variance homogeneity was assessed by the Levene test and the variances were homogeneous ($P > 0.05$), with normal distribution of the data.



Figure 3. Flue gas emission readings

RESULTS and DISCUSSION

In this study, CO₂ emission from burning of biomass obtained from four different residues/ wastes concerning the greenhouse gases due to global warming were determined. The briquettes from those residues were produced by a laboratory type hydraulic briquetting machine and the briquetting pressures varied from 40 MPa to 240 MPa, which were in line with studies described by (Krizan et al., 2015; Zhang and Guo, 2014; Sun et al., 2014) to obtain satisfactory durability

and shape. Moisture content of briquettes was very important for successful extrusion (Oladeji, 2015; Wachira et al., 2015). Moisture content of the material (M12: 10%-12%) in the present study was selected based on EU standards (EN ISO 17225-3, 2015) and previous studies, which reported material moisture contents of between 8%-15% to be suitable for briquetting using hydraulic equipment (Zhang and Guo, 2014; Oladeji, 2015; Coşereanu and Lunguleasa, 2015).

Table 1. Maximum measured CO₂ emissions (%) of briquettes at different pressures

P (MPa)	Tea processing residue	Tomato residue	Persimmon branch	Peach branch
40	2.60±0.00 ^b	3.00± 0.00 ^a	3.10±0.00 ^e	3.50±0.00 ^f
80	2.80±0.00 ^c	2.70±0.00 ^c	3.20±0.00 ^a	3.60±0.00 ^e
120	2.80±0.00 ^c	2.50±0.00 ^d	3.90±0.00 ^c	4.70±0.00 ^d
160	3.00±0.00 ^d	2.60± 0.00 ^b	4.10±0.00 ^b	6.60±0.00 ^b
200	3.10±0.00 ^a	2.60± 0.00 ^b	6.40±0.00 ^d	7.90±0.00 ^c
240	3.10±0.00 ^a	3.70±0.00 ^e	6.40±0.00 ^d	8.90±0.00 ^a

*The difference among the values carrying the same letter at each column is insignificant at $P \leq 0.05$

Flue gas emissions

Many countries are known to suffer from air pollution caused by burning coal for heating purposes, and

burning petroleum-based fuels are known to have high levels of SO_x, NO_x and CO₂ emissions (Ross et al., 2002). Reductions in emissions can be achieved by using biofuel

briquettes made from agricultural residues in combustion chambers in place of coal. The flue-gas emission values of all the briquettes produced from different agricultural residue in the present study indicated their use as solid fuel to be environmentally appropriate. Table 1 shows the maximum CO₂ emission values of the briquettes. CO₂ emission were recorded by a special device after a regular burning was achieved and they were averaged by time during the measurement.

Relationship between briquetting pressures and CO₂ emissions can be expressed as follows:

$$y = a.x^2 + b.x + c \quad \text{Eq. (1)}$$

Where; y is CO₂ emission (%) and x is hydraulic pressing pressure valid for the range 40 to 240 MPa and a, b and c are the coefficients (Table 2). However, a more reliable expression of the mathematical models and their equations along with the R² values were given in Figure 4.

Table 2. Parameters of the mathematical equations for CO₂ emissions

Residue	a	b	c
Tea processing	$-7E-06$	$4.4E-03$	2.44
Tomato	$-9E-05$	$-2.2E-02$	3.82
Persimmon branch	$-7E-05$	$3E-04$	2.87
Peach branch	$-6E-05$	$1.33E-02$	2.57

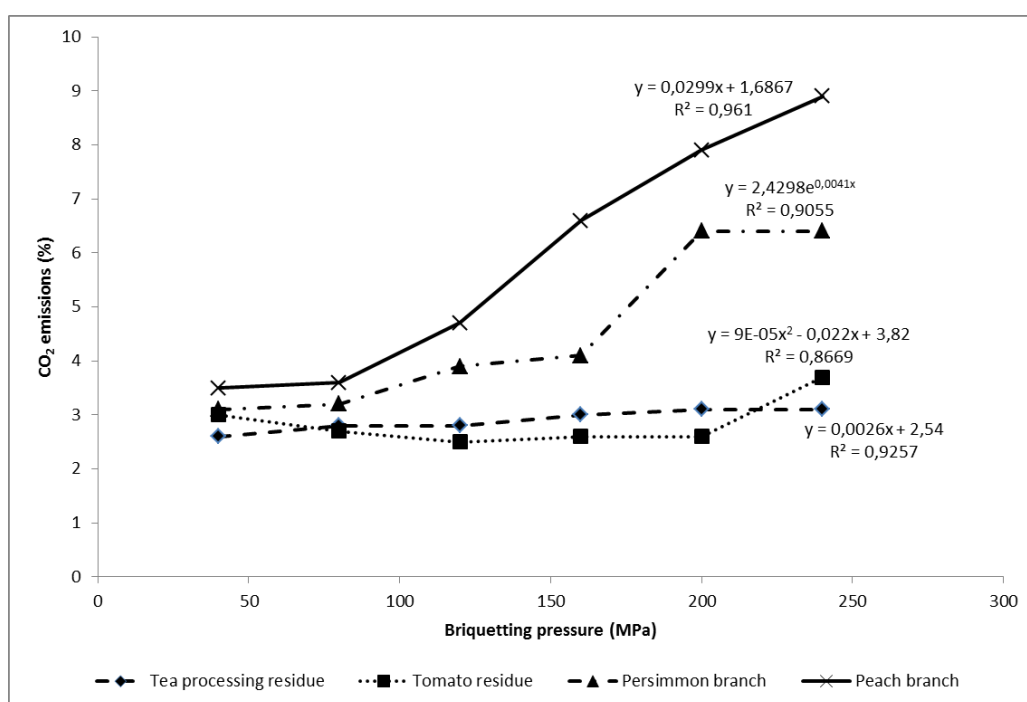


Figure 4. Variations in CO₂ emission of briquettes produced under different pressures

The highest CO₂ emission was obtained at 240 MPa pressure for peach tree pruning briquettes (8.90%), where the lowest was at 120 MPa for the briquettes produced from tomato stalk residues (2.50%). The difference in CO₂ emissions for particular residue is found to be statistically significant ($P > 0.05$). In the meantime, it was determined that CO₂ emissions increased with increase in briquetting pressures. These findings are in line with the studies (Bradna et al., 2017; Bradna et al., 2016) where they measured flue-gas

emissions from biomass pellets produced from rape and wheat straws. The results for CO₂ emissions are also in line with the study done with pruning residues of apple tree (Kazimirova and Opath, 2016), with the studies bio-briquettes and pellets produced from hazelnut and peach tree residues (Gürdil et al., 2016; Gürdil and Melki, 2018). These findings are also in compliance with the results of a research which is done with corn stalk residues (Dok et al., 2019). Where they found the CO₂ emissions of the briquettes 2% to 2.64% and the results

were statistically significant according to the change in particle size of the ground materials. Fortunately, CO₂ emission values of all the bio briquettes in this study fall within the limits (CO_{2max}= 20.3%) of legal Regulations for Air Pollution Control for Heating in Turkey (IKHKY, 2014).

CONCLUSIONS

The present study used a hydraulic briquetting machine to produce cylindrical briquettes with varying briquetting pressures in order to determine the effect of densification to CO₂ emissions of the briquettes. The result of the study revealed that there was a direct proportion between the briquetting pressures and CO₂ emissions. The CO₂ emissions of the bio briquettes produced from tea, tomato, persimmon and peach tree residues ranged from 2.50% to 8.90%. The highest was obtained from peach tree pruning briquettes (at 240 MPa) where the lowest was from the briquettes produced from tomato stalk residues (at 120 MPa).

However, all the emission values for CO₂ were within the defined limits for environmental pollution. In the Regulation on Control of Air Pollution caused by heating (IKHKY), 13% O₂ (% of standard oxygen content) and 20.3% CO_{2max} (% of maximum carbon dioxide in dry residual gas for each fuel). It's well understood from the literature that the higher greenhouse gases emissions in particular CO₂ emissions for this study causes from irregular combustion of solid fuels. Therefore, the options for reducing emissions of incomplete combustion process include uniform fuel supply, sufficiently high temperature in the combustion chamber and sufficient intake of secondary or tertiary air or choice of optimal moisture of biofuel. The briquetting of unused agricultural residues for use as solid biofuel could be useful in meeting today's energy deficits and reducing global warming. In addition, the use of agricultural residues as an alternative energy source can contribute to employment in agricultural regions by promoting the establishment of new, agricultural-based industries. Additional research is important not only for enhancing the quality and quantity of scientific data, but also as a means of focusing public attention on the energy potential of agricultural residues.

ÖZET

Amaç: Bu çalışmada bazı tarımsal artıklardan üretilen biyo-briketlerin baca gazı emisyonları incelenmiştir.

Yöntem ve Bulgular: Briketler, çay (*Camellia sinensis*) işleme tesislerinin kalıntıları, budama hurması

(*Diospyros kaki*) kalıntıları, domates (*Solanum lycopersicum*) sapı ve budama şeftali (*Prunus persica*) ağacının kalıntılarından üretildi. Bu tarımsal artıklar, yatay bir rotaya sahip bir hidrolik briketleme makinesi kullanılarak briketlendi. Katı silindirik briketler, P12: 40 MPa ila 240 MPa arasında değişen, M12 (M12: % 10-% 12) nem içeriğine sahip ve partikül büyüklüğü (PS: 5 mm) olan farklı sıkıştırma basınçları altında üretildi. Biyo briketlerin baca gazı emisyonları ölçüldü.

Genel Yorum: Çalışma, briketleme basınçları arttıkça CO₂ emisyonlarında artan bir eğilim bulmuştur. Domates sapı kalıntılarından üretilen briketler için 120 MPa basınçta en düşük CO₂ emisyonu (% 2.50), şeftali ağacı budamadan üretilen briketler için en yüksek (% 8.90) 240 MPa briketleme basıncında.

Çalışmanın Önemi ve Etkisi: Özellikle, CO₂ gibi en popüler sera gazlarından birinin emisyon değerleri konusuna ve küresel ısınma sorunlarına odaklanılmıştır. Ölçülen tüm CO₂ emisyonları, çevre kirliliği için izin verilen sınırlar dahilinde çıkmıştır.

Anahtar Kelimeler: Biyoyakıt, briket, karbon dioksit, çevre, baca gazı, artık.

REFERENCES

- Angın D, Şensöz S (2006) Effect of drifting gas (N₂) flow on pyrolysis of safflower seed pulps and characterization of liquid product (in Turkish), Fırat Uni. J. Sci. Eng. 18(4): 535-542.
- Bradna J, Malaták J, Hájek D (2016) The properties of wheat straw combustion and use of fly ash as a soil amendment. Agron. Res. 14(4): 1257–1265.
- Bradna J, Malaták J, Velebil J (2017) Impact of differences in combustion conditions of rape straw on the amount of flue gases and fly ash properties. Agron. Res. 15(3): 649–657.
- Chen T, Wu C, Liu R, Fei W, Liu S (2011) Effect of hot vapor filtration on the characterization of bio-oil from rice-husks with fast pyrolysis in a fluidized-bed reactor. Bioresource Technol. 102: 6178-6185.
- Coşoreanu C, Lica D, Lunguleasa A (2015) Investigation on the quality of briquettes made from rarely used wood species, agro-wastes and forest biomass. Pro Ligno 11(1): 32-39.
- Dok M, Acar M, Çelik AE, Atagün G, Akbaş U (2019) Briquetting of corn stalk as a renewable energy source and determination of physical properties of briquettes. MKU. Tar. Bil. Derg. 24 (Özel Sayı) :61-70.

- EN 14774-1 (2009) Solid biofuels - Determination of moisture content - Oven dry method - Part 1: Total moisture - Reference European Committee for Standardization: Management Centre, Avenue Marnix 17, B-1000 Brussels.
- EN ISO 17225-3 (2015) Solid biofuels -Fuel specifications and classes - Part 3: Graded wood briquettes. European Committee for Standardization: Management Centre, Avenue Marnix 17, B-1000 Brussels.
- Grover PD, Mishra SK (1996) Biomass Briquetting: Technology and Practices. FAO Field Document No.46. Bangkok April, Thailand.
- Gürdil GAK, Demirel B, Baz Y, Demirel C (2016) Pelleting hazelnut husk residues for biofuel. In: Proceeding of 6th International Conference on Trends in Agricultural Engineering, September 7-9, 162-165, Prague, Czech Republic.
- Gürdil GAK, Melki S (2018) Determining briquetting parameters for peach tree pruning residues for biofuel. *Fresenius Environ Bulletin* 27(12A): 9083-9090.
- Hájek D, Malaťák J, Hájek P (2013) Combustion of selected biofuels types in furnace turner. *Sci. Agric. Bohemica*. 44: 23–31.
- Hoover AN, Tumuluru JS, Teymour F, Moore J, Gresham G (2014) Effect of pelleting process variables on physical properties and sugar yields of ammonia fiber expansion pretreated corn stover. *Bioresour. Technol.* 164: 128–135.
- IKHKY (2014) Isınmadan kaynaklanan hava kirliliğinin kontrolü yönetmeliği, Ankara. (In Turkish).
- Kaliyan N, Morey RV (2010) Natural binders and solid bridge type binding mechanisms in briquettes and pellets made from corn stover and switchgrass. *Bioresour. Technol.* 101: 1082–1090.
- Karaca C (2017) Hatay ilinin hayvansal gübre kaynağından üretilebilir biyogaz potansiyelinin belirlenmesi. *MKU Zir. Fak. Derg.* 22(1):34-39.
- Karaca C (2019) Agricultural residues potential of Hatay. *MKU. Tar. Bil. Derg.* 24 (Özel Sayı) :9-15.
- Karunanithy C, Wang Y, Muthukumarappan K, Pugalandhi S (2012) Physicochemical characterization of briquettes made from different feedstock. *Biotechnol. Res. Int.* 2012: 1–12.
- Kazimirova V, Opath R (2016) Biomass combustion emissions. *Res. Agric. Eng.* 62: 61-65.
- Križan P, Šooš L, Matúš M, Beniak J, Svátek M (2015) Research of significant densification parameters influence on final briquettes quality. *Wood Research* 60(2): 301-316.
- Malaták J, Bradna J (2017) Heating and emission properties of waste biomass in burner furnace. *Res. Agric. Eng.* 63(1): 16–22.
- Malaťák J, Passian L (2011) Heat-emission analysis of small combustion equipment for biomass. *Res. Agric. Eng.* 57: 37–50.
- McBurney B (1995) A Case Study of a Large Scale Wood Waste Power Generating Plant. *Biologue – Regional Biomass Energy Program Report*. The Official Publication of the National BioEnergy Industries Association, 13: 5– 11.
- Muazu RI, Stegemann JA (2015) Effects of operating variables on durability of fuel briquettes from rice husks and corn cobs. *Fuel Processing Technol.* 133: 137-145.
- Ndindeng SA, Mbassi JEG, Mbacham WF, Manful J, Graham-Acquaah S, Moreira J, Dossou J, Futakuchi K (2015) Quality optimization in briquettes made from rice milling by-products. *Energy Sustain. Dev.* 29: 24–31.
- Oladeji JT (2015) Theoretical aspects of biomass briquetting: a review study. *J. Energ. Technol. Pol.* 5(3): 72-81.
- Ölçüm T (2006) Biodiesel Technology, MSc. Thesis (In Turkish), YTU Ins. Sci. Tech., 81 p.
- Prakash N, Karunanithi T (2008) Kinetic modeling in biomass pyrolysis- a review. *J. Appl. Sci. Res.* 4(12): 1627-1636.
- Ross AB, Jones JM, Chaiklangmuang S, Pourkashanian M, Williams A, Kubica K, Andersson JT, Kerst M, Danihelka P, Bartle KD (2002) Measurement and prediction of the emission of pollutants from the combustion of coal and biomass in a fixed bed furnace. *Fuel*, 81: 571-582.
- Sohni S, Norulaini NAN, Hashim R, Khan SB, Fadhullah W, Omar AKM (2018) Physicochemical characterization of Malaysian crop and agro-industrial biomass residues as renewable energy resources. *Industrial Crops & Products* 111: 642–650.
- Sun B, Yu J, Tahmasebi A, Han Y (2014) An experimental study on binderless briquetting of Chinese lignite: effects of briquetting conditions. *Fuel Process Technol.* 124: 243–248.
- Timung R, Mohan M, Chilukoti B, Sasmal S, Banerjee T, Goud VV (2015) Optimization of dilute acid and hot water pretreatment of different lignocellulosic biomass: a comparative study. *Biomass Bioenerg.* 81: 9-18.
- Ültanır MO (1996) Solar energy and technique at the edge of century (In Turkish). *TÜBİTAK*, 340: 50-55.

- Wachira GG, Gitau AN, Kimani MW, Njoroge BNK (2015) Mechanical properties of saw dust briquettes of eucalyptus tree species of different binders and press machines. Int. J. Emerg. Technol. Adv. Eng. 5(4): 532-538.
- Wang Q, Sarkar J (2018) Pyrolysis behaviours of waste coconut shell and husk biomasses. Int. J. Energy Prod. Mgmt. 3(1): 34-43.
- Zhang J, Guo Y (2014) Physical properties of solid fuel briquettes made from *Caragana korshinskii* Kom. Powder Technol. 256: 293–299.